

INTERNATIONAL
STANDARD

ISO
4589-3

Second edition
2017-04

**Plastics — Determination of burning
behaviour by oxygen index —**

**Part 3:
Elevated-temperature test**

*Plastiques — Détermination du comportement au feu au moyen de
l'indice d'oxygène —*

Partie 3: Essai à haute température

STANDARDSISO.COM : Click to view the full PDF of ISO 4589-3:2017



Reference number
ISO 4589-3:2017(E)

© ISO 2017

STANDARDSISO.COM : Click to view the full PDF of ISO 4589-3:2017



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
5.1 Arrangement	2
5.2 Test chimney	2
5.3 Test specimen holder	3
5.4 Gas supplies	3
5.5 Gas control devices	3
5.6 Oxygen analyser	3
5.7 Flame igniter	4
5.8 Timing device	4
5.9 Fume extraction system	4
6 Calibration and maintenance of equipment	4
7 Preparation of test specimens	4
7.1 Sampling	4
7.2 Test specimen dimensions and preparation	4
7.3 Marking of test pieces	4
7.4 Conditioning	4
8 Procedure	5
8.1 Setting up the apparatus and test specimen	5
8.2 Igniting the test specimen	5
8.3 Assessing burning behaviour	5
8.4 Selecting successive volume fractions of oxygen	5
8.5 Determining the preliminary volume fraction of oxygen	5
8.6 Volume fraction of oxygen changes	6
9 Calculations and expression of results	6
10 Comparison with a specified minimum value of the temperature index at a specified temperature (short procedure)	6
11 Precision	6
12 Test report	6
Annex A (normative) Measurement of flammability temperature (FT)	12
Annex B (informative) Interlaboratory test data on flammability temperature	15
Annex C (informative) Typical test results sheet	16
Bibliography	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 4, *Burning behaviour*.

This second edition cancels and replaces the first edition (ISO 4589-3:1996), which has been technically revised.

A list of all parts in the ISO 4589 series can be found on the ISO website.

Introduction

This document has been prepared to extend the methods available for the determination of flammability by oxygen index (OI) (see ISO 4589-2) to typical elevated temperatures to which a plastic material can be exposed in a service situation. It also provides a method for determining the temperature at which combustion of a small bar of material is just supported in air under certain test conditions; the resulting temperature is termed the flammability temperature.

This document is intended to be used in conjunction with ISO 4589-2 which describes the basic OI test method.

Results obtained in accordance with this document are not applicable to describe or appraise the fire hazard presented by a particular material or shape under actual fire conditions, unless used as one element of a fire risk assessment which takes into account all of the factors which are pertinent to the assessment of the fire hazard of a particular application for the material.

STANDARDSISO.COM : Click to view the full PDF of ISO 4589-3:2017

Plastics — Determination of burning behaviour by oxygen index —

Part 3: Elevated-temperature test

1 Scope

This document specifies methods for determining the minimum volume fraction of oxygen, in a mixture with nitrogen, that will support combustion of small vertical test specimens under specified test conditions over a range of temperatures between 25 °C and 150 °C. The range of temperatures is typically between 40 °C and 150 °C. The results are defined as temperature index values at the test temperature, which is typical of the practical temperature that a plastic material can experience in an overheated service situation.

Methods are provided for testing materials that are self-supporting at the test temperature in the form of vertical bars or sheet up to 10,5 mm thick. However, they are not applicable to form V which requires a supporting frame as defined in ISO 4589-2:2017, Table 2. These methods are suitable for solid, laminated or cellular materials characterized by an apparent density 100 kg/m³ or higher. The methods are also applicable to some cellular materials having an apparent density of less than 100 kg/m³. A method is provided for testing flexible sheet or film materials while supported vertically.

This document also includes a method (see [Annex A](#)) for determining the temperature at which the OI of small vertical test specimens in air is 20,9 % under specified test conditions. The temperature at which this occurs is defined as the flammability temperature (FT) and the method is limited to the determination of temperatures less than 400 °C. The method is not applicable to materials having an OI of <20,9 %.

NOTE 1 It might not be possible to apply these methods satisfactorily to materials that exhibit high levels of shrinkage when heated, e.g. highly oriented thin film.

NOTE 2 For assessing the flame propagation properties of cellular materials of density <100 kg/m³, attention is drawn to the method described in ISO 3582.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4589-1, *Plastics — Determination of burning behaviour by oxygen index — Part 1: General requirements*

ISO 4589-2:2017, *Plastics — Determination of burning behaviour by oxygen index — Part 2: Ambient-temperature test*

ISO 13943, *Fire safety — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4589-1, ISO 13943 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

flammability temperature

FT

temperature at which flaming combustion of a material is supported in air that has a volume fraction of oxygen of 20,9 %

3.2

temperature index

TI

minimum volume fraction of oxygen, in a mixture of oxygen and nitrogen, at a test temperature that supports flaming combustion of a material under specified test conditions

Note 1 to entry: The test temperature will typically be between 40 °C and 150 °C.

3.3

ignition

DEPRECATED: sustained ignition

⟨flaming combustion⟩ initiation of sustained flame

[SOURCE: ISO 13943:2008, 4.188]

4 Principle

A small test specimen is supported vertically in a mixture of oxygen and nitrogen flowing upwards through a transparent heated chimney. The upper end of the specimen is ignited, and the subsequent burning behaviour of the specimen is observed to compare the period for which burning continues, or the length of specimen burnt with specified limits for such burning. By testing a series of specimens in different volume fractions of oxygen, the minimum volume fraction of oxygen is estimated. General requirements for the apparatus and test method are given in ISO 4589-1.

5 Apparatus

5.1 Arrangement

The apparatus specified in [5.2](#) to [5.6](#) shall be arranged as indicated in [Figures 1](#) to [4](#), as appropriate.

5.2 Test chimney

The test chimney shall consist of two concentric heat-resistant glass tubes supported vertically between an insulating top plate and a base through which oxygen-containing gas mixtures can be introduced. The chimney is provided with a heating element suitable for use in conjunction with a preheater for heating the incoming gas mixture. This is to maintain the test atmosphere within the inner tube in the vicinity of the test specimen at within ± 3 °C of any specific test temperature up to, and including 125 °C and at within ± 5 °C of any higher test temperature at which the equipment is intended to be used. The heating element shall not impede adequate observation of a test specimen under test.

The preferred dimensions of the inner tube are 450 mm to 500 mm minimum height, and 75 mm to 100 mm diameter cylindrical bore. The upper outlet should preferably be restricted as necessary by an overhead cap having an outlet small enough to produce an exhaust velocity of at least 90 mm/s at 23 °C ± 2 °C from a flow rate within the chimney of 40 mm/s at 23 °C ± 2 °C (see Note). The height of the outer tube should be similar to that of the inner tube, and the radial clearance between the inner and outer

tubes should be between 5 mm and 10 mm. Chimneys of other dimensions, with or without restricted outlets, may be used if shown to give equivalent results.

The bottom of the chimney, or the base upon which the chimney is supported, shall incorporate a means for distributing evenly the gas mixture entering the inner tube. A satisfactory means comprises beads of diameter between 3 mm and 5 mm in a layer between 80 mm and 100 mm deep. Other devices, such as radial manifolds, may be used if shown to give equivalent results.

A porous screen may be mounted below the level of the test piece holder to prevent falling combustion debris from fouling the gas entry and distribution paths.

The chimney support may incorporate a levelling device and indicator to facilitate vertical alignment of the chimney, and a test piece supported therein. A dark background may be provided to facilitate observation of flames within the chimney.

NOTE For inner tubes of diameter 75 mm to 100 mm, a cap converging to an outlet of diameter 40 mm at a level at least 10 mm above the top of the cylindrical chimney is satisfactory. For such tubes also, an electrical-resistance heating element dissipating up to about 1 000 W and helically wound around the outer surface of the tube with a graded distribution of winding pitch so that the temperature is evenly distributed is suitable in conjunction with a preheater comprising a cylindrical ceramic body with longitudinal holes and containing a heating element dissipating up to about 1 000 W with regulating controls which can be operated separately from those of the heater windings on the chimney tube. If the target test condition is 150 °C or less, a preheater is not necessary; apparatus of more simple structure can be used.

5.3 Test specimen holder

The test specimen holder specified in ISO 4589-2:2017, 5.2 shall be used.

The transfer device (see [Figure 4](#)) can be used for moving a specimen loaded specimen holder into the test chimney.

5.4 Gas supplies

The gas supplies specified in ISO 4589-2:2017, 5.3 shall be used.

Because damage can occur to the chimney heater and preheater if energized while no gas flows through them, it is recommended that a gas-flow or pressure-sensing device is incorporated in the gas supply lines and is coupled to the heater power-control circuits.

To economize purified oxygen and nitrogen, it is recommended that an air pump is provided to supply air instead of oxygen and/or nitrogen, at the appropriate flow rate, during periods when specimens are not being tested.

5.5 Gas control devices

The gas supplies specified in ISO 4589-2:2017, 5.4 shall be used, except that the flow rate shall be 40 mm/s \pm 0,8 mm/s at 23 °C.

A thermocouple (see [Figure 1](#), Key 9) shall be provided for checking or ensuring that the temperature of the gas mixture in the chimney is in accordance with [5.2](#). If this involves an internal probe, its position and profile shall be designed to minimize induction of turbulence within the chimney.

NOTE Systems of measurement and control that have proved satisfactory are listed in ISO 4589-2:2017, 5.4.

5.6 Oxygen analyser

The oxygen analyser specified in ISO 4589-2:2017, 5.5 shall be used.

5.7 Flame igniter

The flame igniter specified in ISO 4589-2:2017, 5.6 shall be used.

5.8 Timing device

The timing device specified in ISO 4589-2:2017, 5.7 shall be used.

5.9 Fume extraction system

The fume extraction system specified in ISO 4589-2:2017, 5.8 shall be used.

6 Calibration and maintenance of equipment

Calibrate and maintain the equipment periodically in accordance with the instructions given in ISO 4589-2:2017, Annex A so that the maximum interval between recalibration and use conforms to the periods stated in ISO 4589-2:2017, Table 1, except that the accuracy of checking the flow rate shall be $\pm 0,8 \text{ mm/s}$.

7 Preparation of test specimens

7.1 Sampling

Sampling shall be in accordance with ISO 4589-2:2017, 7.1.

For the flammability temperature procedure (see [Annex A](#)), at least 10 test specimens shall be provided. If a test specimen is not self-supporting at the temperature of the test, it shall be provided with external support by the use of a $0,55 \text{ mm} \pm 0,05 \text{ mm}$ diameter nickel-chromium alloy wire with a maximum working temperature of $1\ 100 \text{ }^\circ\text{C}$, and secured by ties of copper wire of $0,20 \text{ mm} \pm 0,02 \text{ mm}$ diameter. These shall be positioned as shown in [Figure 5](#). See [Annex B](#) for round-robin analysis of the effects of variation of the test specimen holder.

Another practice is to support the test piece between two capillary glass tubes, the assembly being lightly bound together with a single tie of fine nichrome or stainless-steel wire (nominally $200 \mu\text{m}$ gauge), and held in a small standard clamp. This non-standard practice should be used carefully and recorded in the test report.

7.2 Test specimen dimensions and preparation

With the exception of form V, test specimen dimensions shall conform to, and specimen preparation shall be in accordance with, ISO 4589-2:2017, 7.2.

7.3 Marking of test pieces

Marking of the test specimens shall be in accordance with ISO 4589-2:2017, 7.3.

7.4 Conditioning

Conditioning shall be in accordance with ISO 4589-2:2017, 7.4.

8 Procedure

8.1 Setting up the apparatus and test specimen

8.1.1 Position a temperature sensor in the position to be occupied by the top of a test specimen.

Adjust the electrical power to the chimney heater and preheater to give the test temperature, with the gas controls set to give a gas velocity within the chimney of $40 \text{ mm/s} \pm 0,8 \text{ mm/s}$ at 23°C . The flow rate shall be estimated by using the formula found in ISO 4589-2:2017, A.2.

8.1.2 Select an initial volume fraction of oxygen to be used. When possible, base this on experience of results for similar materials. Alternatively, try to ignite a test specimen in the chimney supplied with mixed gas and heated to the test temperature, and note the burning behaviour. If the specimen burns rapidly, select an initial volume fraction of about 18 % of oxygen; if the test specimen burns gently or unsteadily, select an initial oxygen volume fraction of about 21 %; if the specimen does not continue to burn in air, select an initial volume fraction of at least 25 %, depending upon the difficulty of ignition or the period of burning before extinguishing in air.

8.1.3 When the temperature in the test chimney is stable and in accordance with the limits given in [5.2](#), mount a specimen in the centre of the chimney so that the top of the specimen is at least 100 mm below the open top of the chimney, and the lowest exposed part of the specimen is at least 100 mm above the top of the gas distribution device at the base of the chimney.

8.1.4 Preheat the specimen for $240 \text{ s} \pm 10 \text{ s}$ for it to reach a temperature within the applicable test temperature tolerance before ignition.

8.1.5 Set the gas mixing and flow controls so that an oxygen/nitrogen mixture at 23°C , containing the desired volume fraction of oxygen, flows within the chimney at $40 \text{ mm/s} \pm 0,8 \text{ mm/s}$. Let the gas flow purge the chimney for at least 30 s prior to ignition of each specimen, and maintain the flow without change during ignition and combustion of each specimen. The flow rate shall be estimated by using the formula found in ISO 4589-2:2017, A.2.

Record the volume fraction of oxygen used, which is measured by an oxygen analyser or calculated in accordance with the formulae given in ISO 4589-2:2017, Annex B.

8.2 Igniting the test specimen

Ignite the specimen in accordance with ISO 4589-2:2017, 8.3 using procedure A or procedure B.

8.3 Assessing burning behaviour

The burning behaviour of individual test specimens shall be assessed in accordance with ISO 4589-2:2017, 8.4, except that the test temperature shall be determined by this document.

8.4 Selecting successive volume fractions of oxygen

The volume fraction of oxygen required for the purpose of [8.5](#) to [8.6](#) shall be calculated in accordance with ISO 4589-2:2017, Annex B.

Select successive volume fractions of oxygen in accordance with ISO 4589-2:2017, 8.5.

8.5 Determining the preliminary volume fraction of oxygen

Determine the preliminary volume fraction of oxygen in accordance with ISO 4589-2:2017, 8.6.

8.6 Volume fraction of oxygen changes

Make volume fraction of oxygen changes in accordance with ISO 4589-2:2017, 8.7.

9 Calculations and expression of results

Calculate the temperature index at the test temperature in accordance with ISO 4589-2:2017, 9.1, and determine k in accordance with ISO 4589-2:2017, 9.2. Determine the standard deviation of the oxygen volume fraction measurements in accordance with ISO 4589-2:2017, 9.3.

10 Comparison with a specified minimum value of the temperature index at a specified temperature (short procedure)

Carry out the procedure in accordance with ISO 4589-2:2017, Clause 10, with the exception that the test temperature will be the specified elevated temperature.

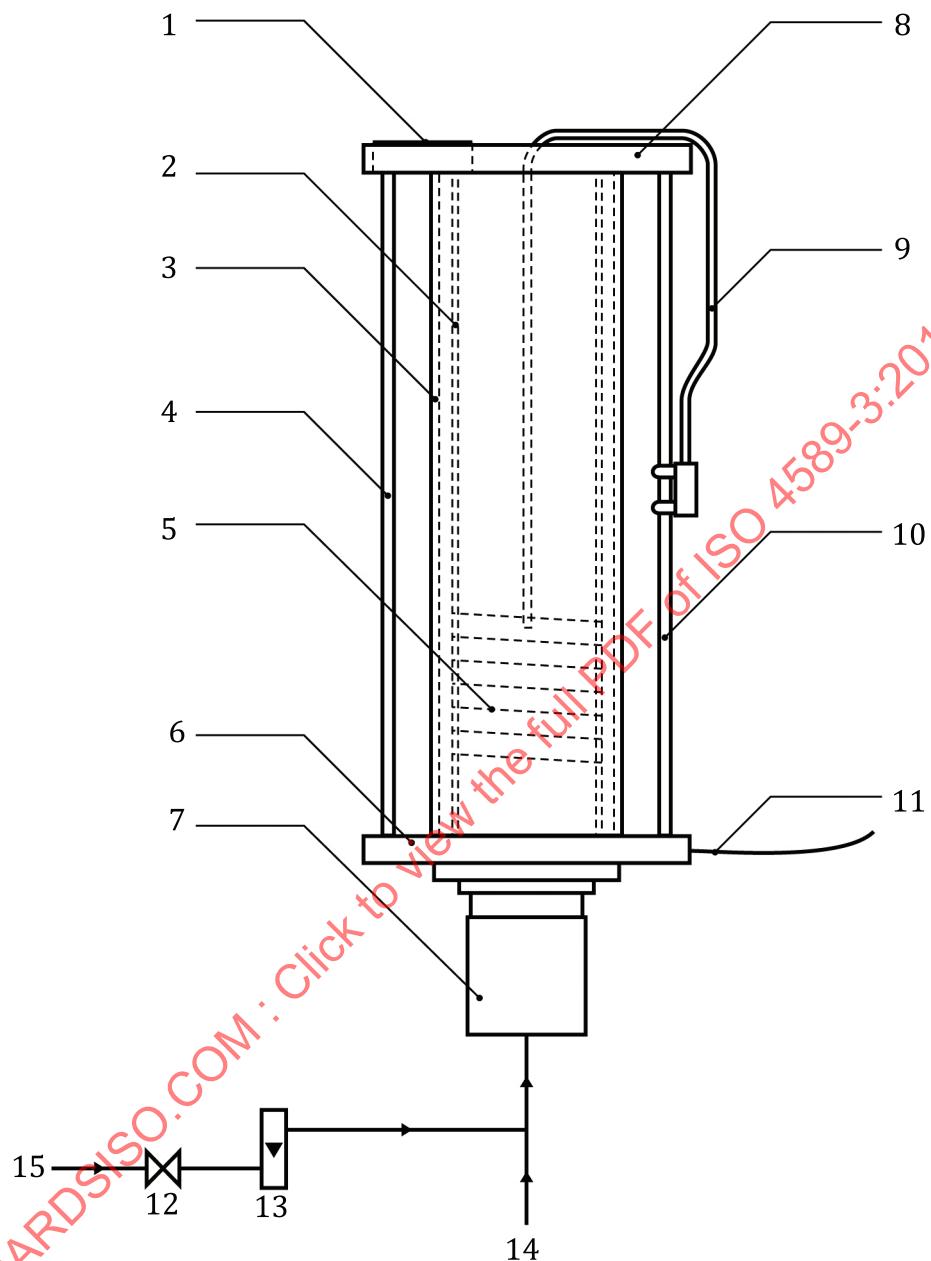
11 Precision

No precision data for these methods of test are currently available. Interlaboratory trials data are being obtained and it is intended that a precision statement be added at the first revision following their collation.

12 Test report

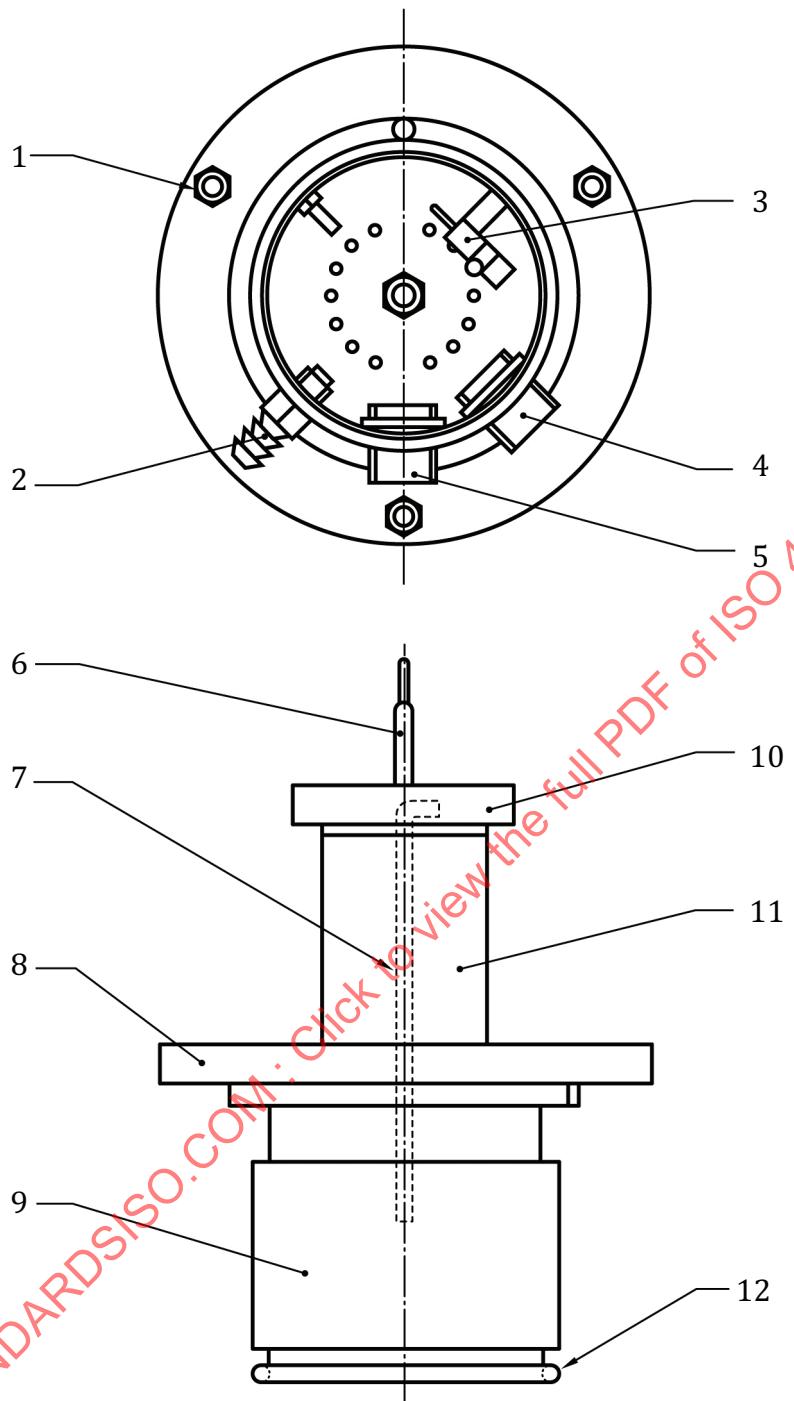
The test report shall include the following information:

- a) a reference to this document, i.e. ISO 4589-3;
- b) a statement that the test results relate only to the behaviour of the test specimens under the conditions of this test, and that these results are not to be used to infer the fire hazards of the material in other forms or under other fire conditions;
- c) all details necessary for identification of the material tested, including, where relevant, the type of material, its density, its previous history and the specimen orientation with respect to any anisotropy in the material or sample;
- d) the test specimen form (I, II, III, IV and VI) and dimensions;
- e) the method of specimen support, e.g. self-supporting or by use of nickel-chromium alloy wire;
- f) the ignition procedure used (A or B) and the igniter used, if other than the standard propane flame;
- g) the temperature index;
- h) the test temperature;
- i) the estimated standard deviation and the oxygen volume fraction increment used, if other than 0,2 %;
- j) a description of any relevant ancillary characteristics or behaviour, such as charring, dripping, severe shrinkage, erratic burning or afterglow;
- k) any deviations from the requirements of this document.

**Key**

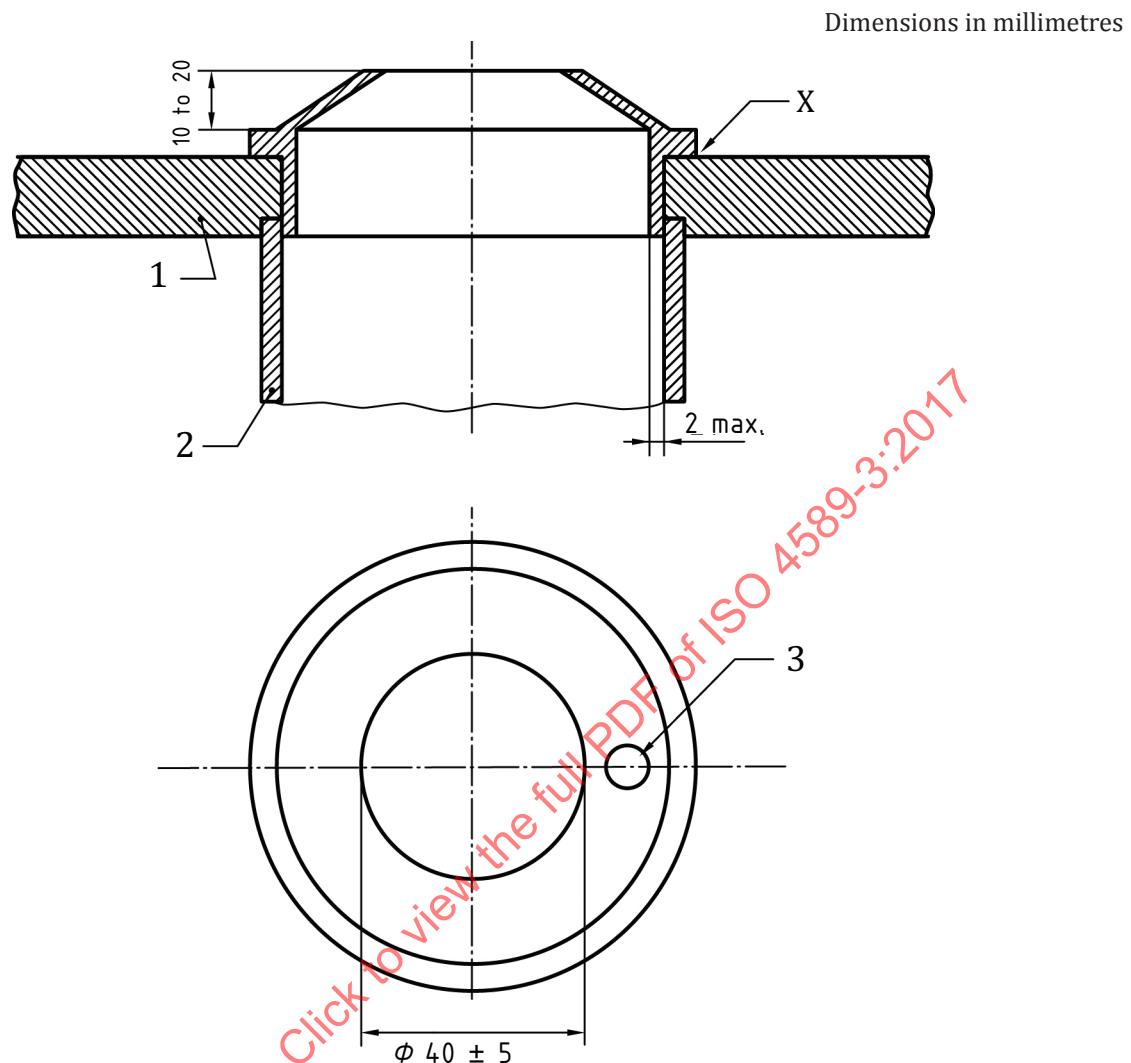
1	1,5 mm diameter mineral-insulated control thermocouple for column heater	9	3 mm diameter mineral-insulated chromel-alumel thermocouple clad in stainless steel
2	glass test column	10	tie rod
3	outer glass column	11	column heater power cable
4	tie rod	12	on/off valve
5	nickel-chromium alloy wire wound to form column heater	13	flowmeter
6	bottom end-plate	14	gas control devices (see ISO 4589-2:2017, 5.4)
7	preheater and base of assembly	15	air
8	top end-plate		

Figure 1 — Typical heated chimney

**Key**

1	fixing nuts for fastening preheater base to bottom end-plate of test chimney	7	0,5 mm diameter mineral-insulated thermocouple for heater
2	air inlet pipe	8	base of preheater
3	pressure warning switch assembly	9	metal base cylinder
4	preheater power plug	10	removable gauze
5	thermocouple plug	11	preheater assembly
6	spigot for mounting specimen holder	12	O-ring

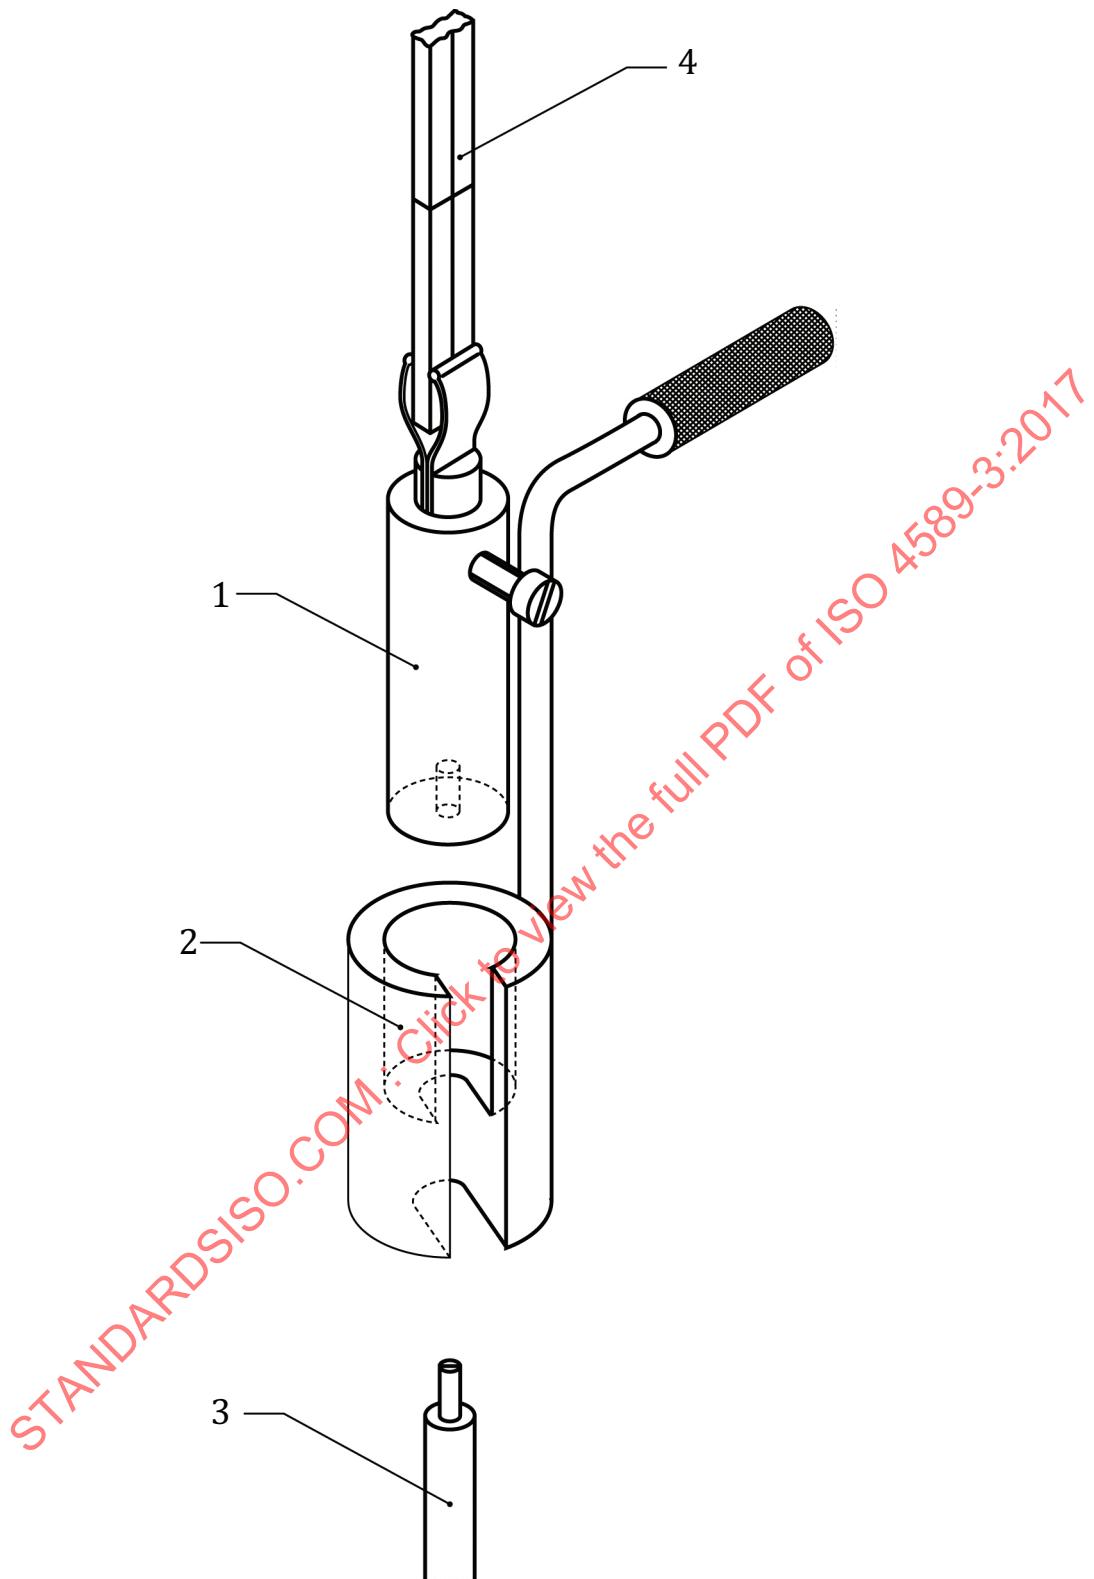
Figure 2 — Typical form of preheater and base of assembly for test chimney

**Key**

- 1 top plate
- 2 inner chimney
- 3 a hole for inserting a thermocouple (if necessary)

NOTE "X" indicates need for clearance to accommodate differential thermal expansion.

Figure 3 — Typical chimney outlet restrictor

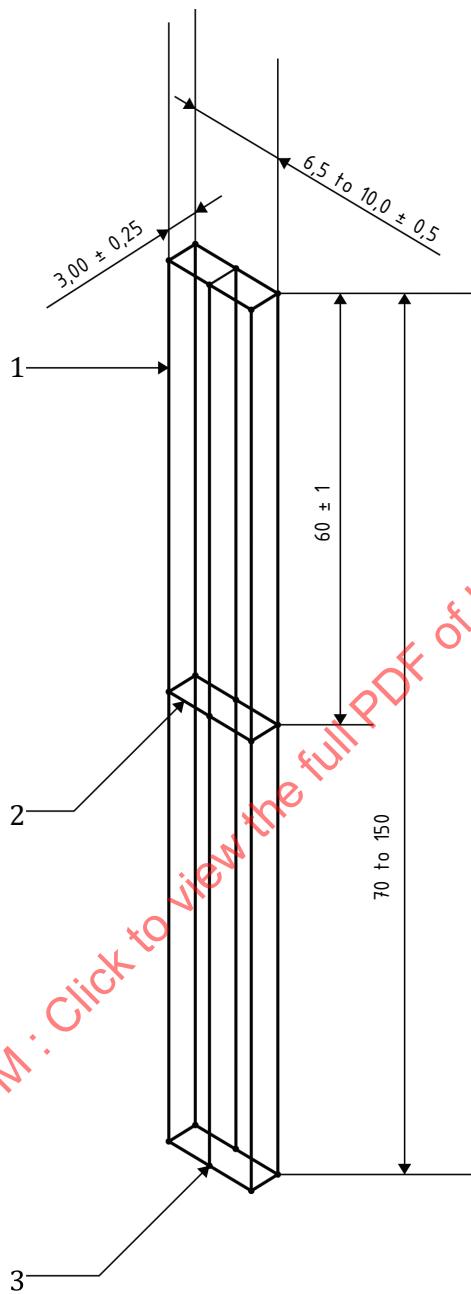


Key

- 1 removable specimen holder
- 2 transfer device
- 3 specimen-mounting post fixed to preheater assembly
- 4 test specimen support (see [Figure 5](#))

Figure 4 — Typical specimen-holder transfer tool

Dimensions in millimetres

**Key**

- 1 vertical nickel-chromium alloy wires, $\varnothing 0,55 \text{ mm} \pm 0,05 \text{ mm}$
- 2 external copper tie wire, $\varnothing 0,20 \text{ mm} \pm 0,02 \text{ mm}$
- 3 a tie wire between the central vertical wires is optional at the lower end of the support

Figure 5 — Test specimen support

Annex A (normative)

Measurement of flammability temperature (FT)

A.1 Setting up the apparatus

A.1.1 Maintain the room or enclosure used for the test at ambient conditions of $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ and $50\% \pm 5\%$ r.h., unless each test specimen is conditioned in accordance with 7.4 until immediately prior to use, in which case ambient humidity control to $50\% \pm 5\%$ r.h. is optional.

A.1.2 Set the flow controls so that air is flowing within the chimney at a velocity of $40\text{ mm/s} \pm 0,8\text{ mm/s}$ when measured at $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ (see 8.1.5). Carry out the remainder of the test procedure using this setting.

The gas velocity, F , may be calculated from the following [Formula \(A.1\)](#):

$$F = \left(\frac{4}{\pi} \right) \times 10^6 \left(\frac{q_v}{D^2} \right) = 1,27 \times 10^6 \left(\frac{q_v}{D^2} \right) \quad (\text{A.1})$$

where

F is the flow rate within the chimney, expressed in millimetres per second (mm/s);

q_v is the total gas flow at $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ within the chimney, expressed in litres per second (l/s);

D is the diameter of the bore of the chimney, expressed in millimetres (mm).

A.1.3 Allow the gas mixture to flow for at least 30 s to purge the system.

A.1.4 Set the column temperature at a desired value using the column and preheater controls. This temperature shall be less than $400\text{ }^{\circ}\text{C}$. Using the thermocouple, adjust the controls to obtain a temperature gradient of less than $5\text{ }^{\circ}\text{C}$ between the position of the top of the test specimen and 50 mm below this position. Resite the thermocouple 25 mm below the top of the test specimen. Allow the temperature to stabilize.

The adjustment of these independent controls should be such that the preheater raises the incoming air temperature at the base of the column to approximately that of the column itself. The use of widely differing settings between preheater and column temperatures can contribute to variation in the FT value obtained.

It can be helpful to perform preliminary tests during which the temperature is varied to establish an approximate value for the FT. Results of such tests should not be included in the estimation of the FT.

A.1.5 Using a test specimen holder preheated to the column temperature, insert a test specimen in the test specimen holder and place this in the chimney using the transfer tool. With the exception of form V, test specimen dimensions shall conform to, and specimen preparation shall be in accordance with ISO 4589-2:2017, 7.2. With the thermocouple positioned so that it is immediately adjacent to, but not touching the test specimen as shown in [Figure 1](#), leave the apparatus for $240\text{ s} \pm 10\text{ s}$ to permit temperature stabilization, and then record the indicated air temperature.

A.1.6 If the recorded air temperature after stabilization is higher than 10 °C, different from the temperature set in [A.1.4](#), repeat the procedures of [A.1.4](#) and [A.1.5](#) (see Notes 1 and 2). If otherwise, move the thermocouple away from the specimen and proceed immediately in accordance with [A.2.1](#).

NOTE 1 It can be helpful also to preheat the transfer tool if an excessive temperature difference is induced by a chilling effect from that tool.

NOTE 2 Use of periods other than 240 s ± 10 s between introduction of the test specimen and the initial application of the igniter in accordance with [A.2.1](#) can lead to non-comparable results when testing materials for which the FT is sensitive to the period of exposure to elevated temperature.

A.2 Igniting the test specimen

A.2.1 Apply the ignition source so that approximately 6 mm of the flame impinges on the top of the test specimen. As the test specimen burns, lower the ignition source to maintain the flame impingement of approximately 6 mm. Apply the flame for 15 s ± 1 s to ignite the test specimen. Upon removal of the ignition flame, start the timer.

A.2.2 Do not adjust any of the controls after ignition of the test specimen.

A.3 Assessing burning behaviour

A.3.1 Observe the burning behaviour of the test specimen. Record whether the flame is extinguished before either of the relevant criteria from ISO 4589-2:2017, Table 3 is satisfied, i.e. the minimum period of burning is exceeded or the minimum length of the test specimen is burnt. Alternatively, when either of the criteria is exceeded, extinguish the flame and record the response of the test specimen.

A.3.2 Remove the used test specimen and any debris.

A.4 Selecting successive test temperatures

Depending upon the behaviour of preceding test specimens, select the temperature for the following test. Reduce the temperature if the burning of the test specimen exceeded either the period or the length specified (see ISO 4589-2:2017, Table 3) or increase the temperature if neither criterion was exceeded.

A.5 Determining flammability temperature

A.5.1 Continue repeating the procedure from [A.1.3](#) to [A.4](#) inclusive until the FT is established to within an increment of 5 °C, as the lowest column temperature as recorded in [A.1.5](#), at which the test specimen exceeds at least one of the test criteria.

Increments of >5 °C may be used to establish an approximate value of FT.

A.5.2 Determine at least three values for the FT of the material by carrying out the procedure from [A.1.3](#) to [A.5.1](#) inclusive at least three times.

A.5.3 Calculate and record the FT of the material as the mean value of the three or more values determined in accordance with [A.5.2](#). Express it as the mean value when rounded to the nearest 1 °C, with an exactly intermediate result being rounded downwards.

A.6 Test report

The test report shall include the following information:

- a) a reference to this document, i.e. ISO 4589-3;
- b) a statement that the test results relate only to the behaviour of the test specimens under the conditions of this test and that these results are not to be used to infer the fire hazards of the material in other forms or under other fire conditions;
- c) all details necessary for identification of the material tested, including, where relevant, the type of material, its density, its previous history and the specimen orientation with respect to any anisotropy in the material or sample;
- d) the test specimen form (I, II, III, IV or VI) and dimensions;
- e) the method of specimen support, e.g. self-supporting or by use of nickel-chromium alloy wire;
- f) the igniter used, if other than the standard propane flame;
- g) the flammability temperature;
- h) a description of any relevant ancillary characteristics or behaviour such as charring, dripping, severe shrinkage, erratic burning or afterglow;
- i) any deviations from the requirements of this document.

STANDARDSISO.COM : Click to view the full PDF of ISO 4589-3:2017