

INTERNATIONAL STANDARD

ISO
8827

First edition
1988-10-15



INTERNATIONAL ORGANIZATION FOR STANDARDIZATION
ORGANISATION INTERNATIONALE DE NORMALISATION
МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ

Implants for surgery — Staples with parallel legs for orthopaedic use — General requirements

Implants chirurgicaux — Agrafes à pattes parallèles à usage orthopédique — Spécifications générales

Reference number
ISO 8827:1988 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 8827 was prepared by Technical Committee ISO/TC 150, *Implants for surgery*.

Users should note that all International Standards undergo revision from time to time and that any reference made herein to any other International Standard implies its latest edition, unless otherwise stated.

Implants for surgery – Staples with parallel legs for orthopaedic use – General requirements

1 Scope and field of application

This International Standard covers general requirements and the designation of dimensions and tolerances of staples with parallel legs intended for use in orthopaedic surgery.

NOTE — The annex gives guidance on the selection and use of staples and does not form an integral part of this International Standard.

2 References

ISO 5832, *Implants for surgery – Metallic materials –*

Part 1: Wrought stainless steel.

Part 3: Wrought titanium 6-aluminium 4-vanadium alloy.

Part 4: Cobalt-chromium-molybdenum casting alloy.

Part 5: Wrought cobalt-chromium-tungsten-nickel alloy.

ISO 6018, *Implants for surgery – General requirements for marking, packaging and labelling.*

ISO 6892, *Metallic materials – Tensile testing.*

3 Design

3.1 Radius of curvature

The internal radius of curvature of staples made from wire shall be not less than 2 mm or the diameter of the wire, whichever is the greater. The curve shall have a smooth contour.

3.2 Points

Points of staples shall be conical, trocar-shaped, spear-shaped or flattened (i.e. tapered in one plane).

3.3 Legs

The legs shall be parallel.

NOTES

1 Examples of typical forms of staples used in orthopaedic surgery are illustrated in figure 1. Figure 1 shows the designation of dimensions and gives nomenclature; it does not purport to specify design requirements and does not otherwise form part of the requirements for staples as laid down in this International Standard.

2 Staples are commonly of circular, oval or modified rectangular cross-section, although other forms may be used. If staples are made from wire, wire 2,5 mm in diameter is commonly used. Greater strength may be achieved by using an oval cross-section, generally of the order of 4 mm x 2 mm, or by reinforcing the bend area with webs [see figure 1b)]. The legs may be plain, or have barbs or other surface features or treatments.


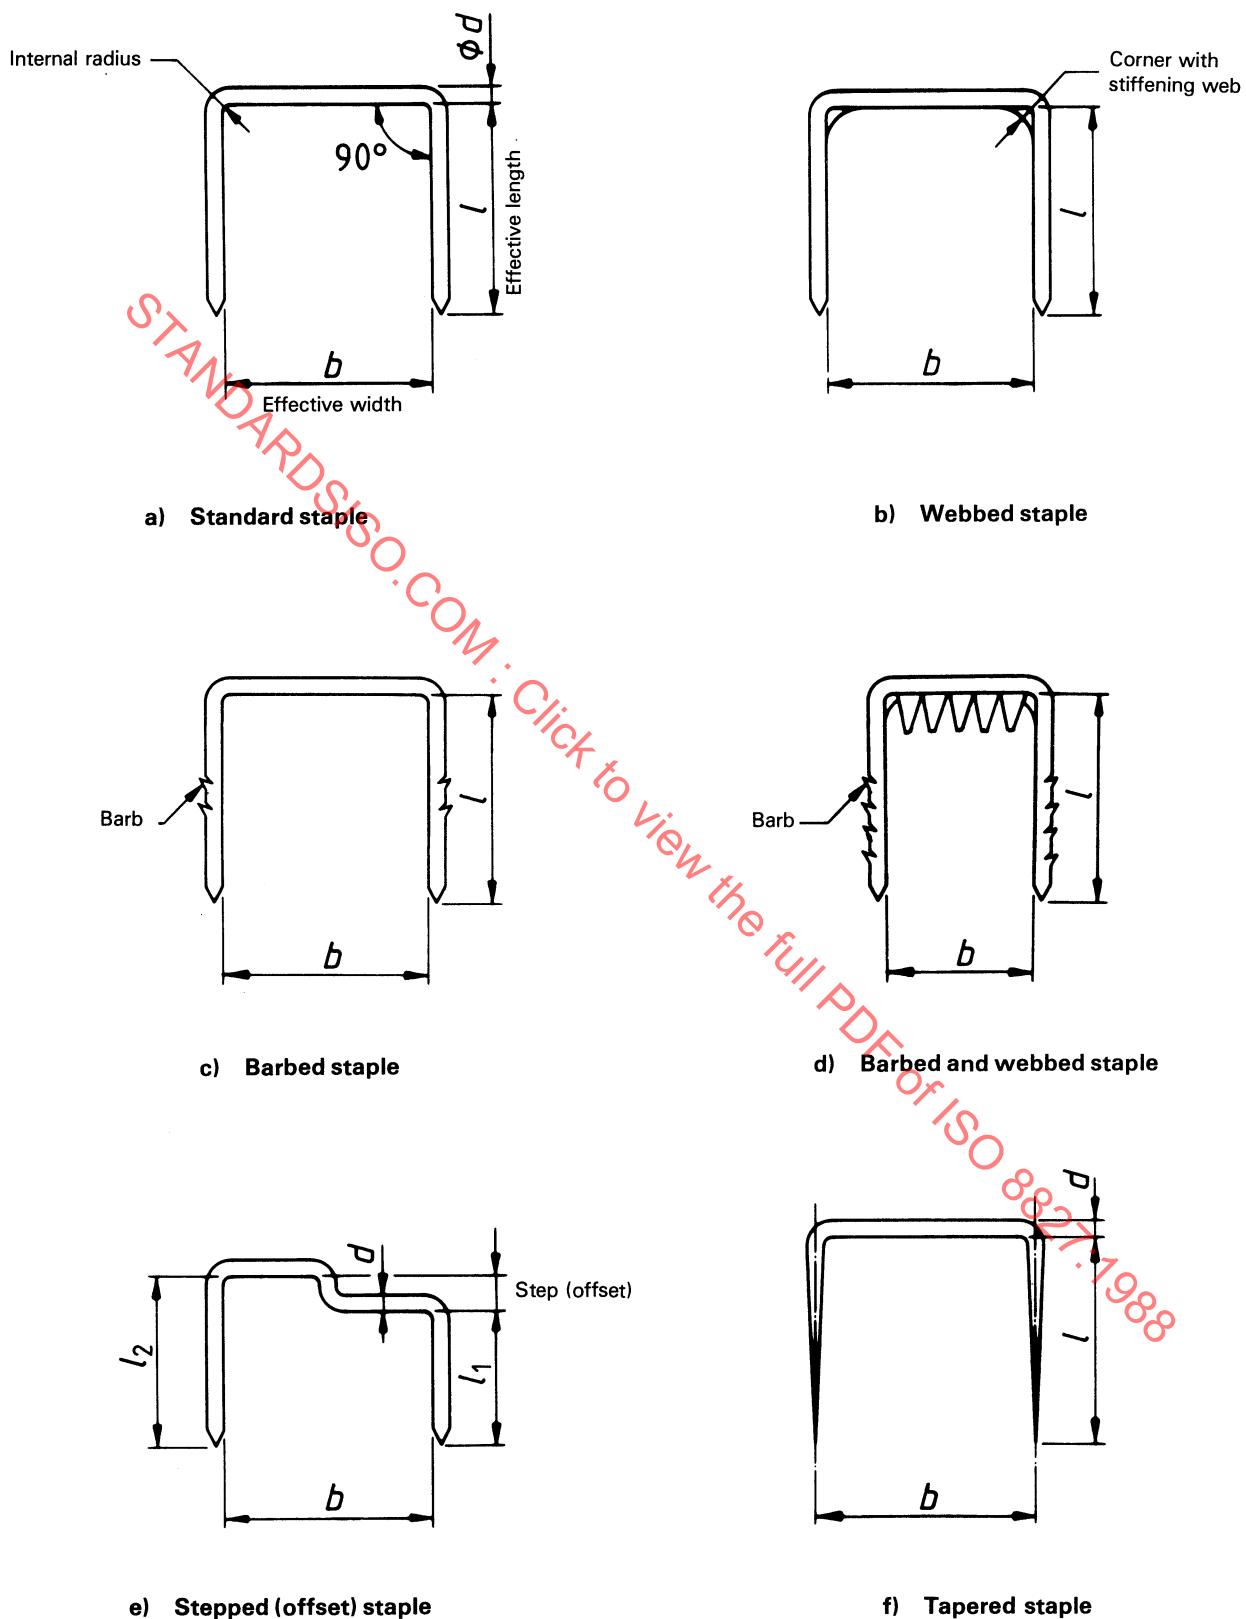


Figure 1 — Examples of typical forms of staples for use in orthopaedic surgery

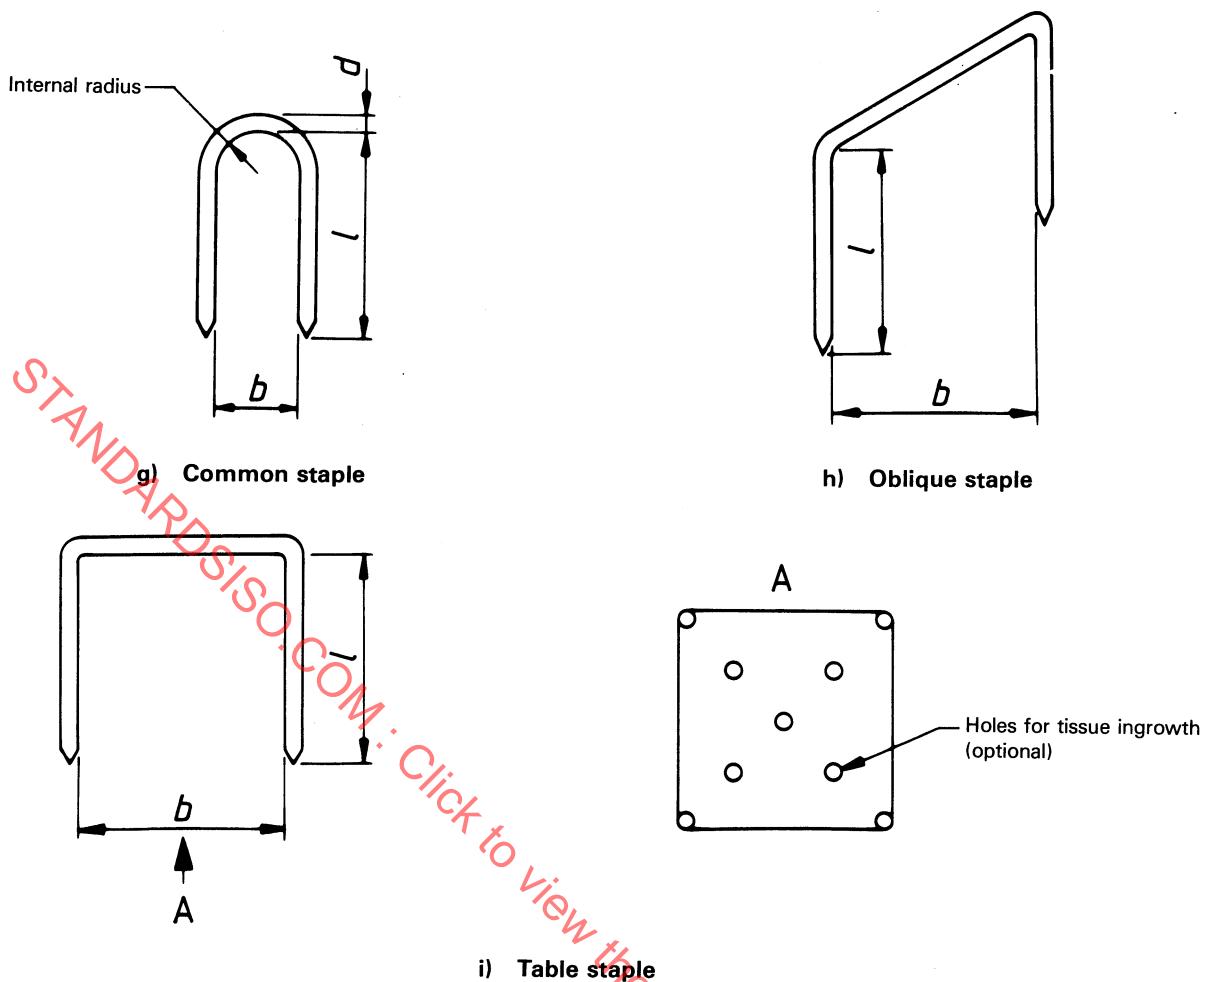

NOTE — The figures illustrate various types of staple for the purpose of defining the relevant dimensions and features, but the illustrations do not otherwise form part of the requirements for staples as laid down in this International Standard.

Figure 1 — Examples of typical forms of staples for use in orthopaedic surgery (concluded)

4 Size designation

The size of staples shall be designated by effective length, l , effective width, b , and diameter, d , respectively (see figure 1), expressed in millimetres, as follows:

$25 \times 20 \times 1$

Staples with legs of unequal length shall have the effective length of each leg stated.

Staples of oval or modified rectangular cross-section shall have the major and minor cross-sectional dimensions stated.

5 Tolerances

The effective length and effective width of staples shall be in accordance with the nominal dimensions ± 1 mm.

The axis of one leg of the staple shall be parallel, with respect to the axis of the other leg, within a cylindrical tolerance zone 0,5 mm in diameter (see figure 2).

In the case of table staples [see figure 1i)], the parallelism tolerances shall apply to each and every pair of legs.

6 Materials

6.1 General

Staples shall be made from austenitic stainless steel, cast cobalt-chromium-molybdenum alloy, wrought cobalt-chromium-tungsten-nickel alloy, or wrought titanium alloy. When produced from wire or by casting, the material shall satisfy the requirements laid down in 6.2, 6.3, 6.4 and 6.5.

6.2 Austenitic stainless steel wire

6.2.1 Composition

Wire used in the manufacture of staples shall be made from austenitic stainless steel in accordance with ISO 5832-1 and shall comply with the requirements of the corrosion resistance test specified in ISO 5832-1.

Tolerance in millimetres

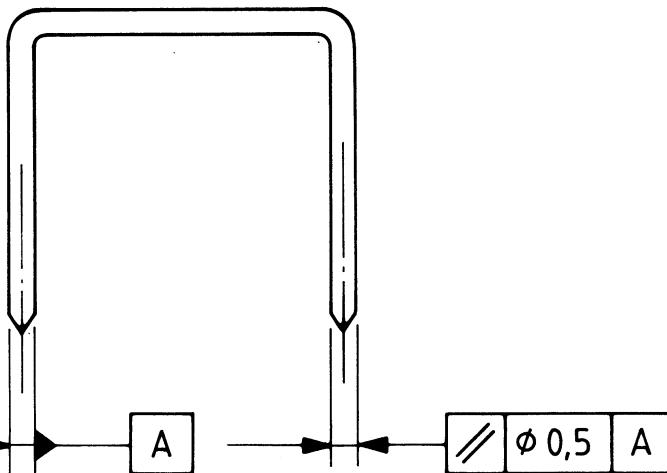


Figure 2 — Parallelism of legs

6.2.2 Tensile properties

When tested in accordance with ISO 6892, the tensile properties of the wire in the as-drawn (coiled) condition and after straightening shall be as given in the table.

Table — Tensile properties of wire made from austenitic stainless steel

Diameter mm	Minimum tensile strength		Percentage elongation after fracture min.
	As-drawn (coiled) condition	Straightened condition	
N/mm ²	N/mm ²	%	
1	1 550	1 400	3
1,6	1 550	1 400	3
2	1 550	1 400	3
2,5	1 550	1 400	3
3,15	1 400	1 325	5
4	1 400	1 240	5

NOTE — The wire may have been subjected to a stress-relieving heat treatment at a temperature not exceeding 450 °C.

6.3 Cast cobalt-chromium-molybdenum alloy

6.3.1 Composition

Cast cobalt-chromium-molybdenum alloy used in the manufacture of staples shall comply with the requirements laid down in ISO 5832-4, except for the tensile properties of the material which shall comply with the requirements laid down in 6.3.2.

6.3.2 Tensile properties

When tested in accordance with ISO 6892, the tensile strength of the staples in the as-cast condition shall be not less than

700 N/mm², the proof stress of non-proportional elongation $R_{p0,2}$ shall be not less than 500 N/mm² and the percentage elongation after fracture shall be not less than 8 %.

6.4 Wrought cobalt-chromium-tungsten-nickel alloy

6.4.1 Composition

Wrought cobalt-chromium-tungsten-nickel alloy used in the manufacture of staples shall comply with the requirements laid down in ISO 5832-5, except for the tensile properties of the material which shall comply with the requirements laid down in 6.4.2.

6.4.2 Tensile properties

When tested in accordance with ISO 6892, the tensile strength of the cold drawn wire used for staples shall be not less than 1 280 N/mm² and the percentage elongation after fracture shall be not less than 7 %.

6.5 Wrought titanium alloy

6.5.1 Composition

Wire made of wrought titanium 6-aluminium 4-vanadium alloy shall comply with the requirements laid down in ISO 5832-3, except for the tensile properties of the material which shall comply with the requirements laid down in 6.5.2.

6.5.2 Tensile properties

When tested in accordance with ISO 6892, the tensile strength of the wires used for staples shall be within the range from 1 150 N/mm² to 1 400 N/mm² and the percentage elongation after fracture shall be not less than 3 %.